



MOCVD Equipment



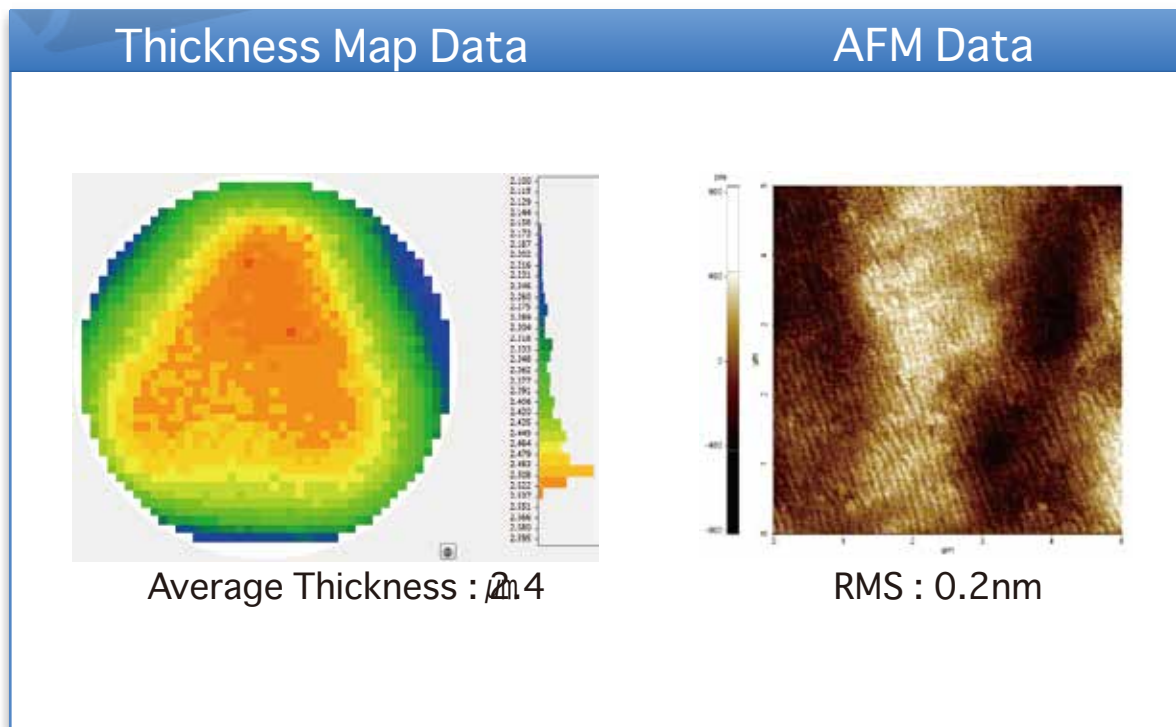

Bowing Measurement by Etamax

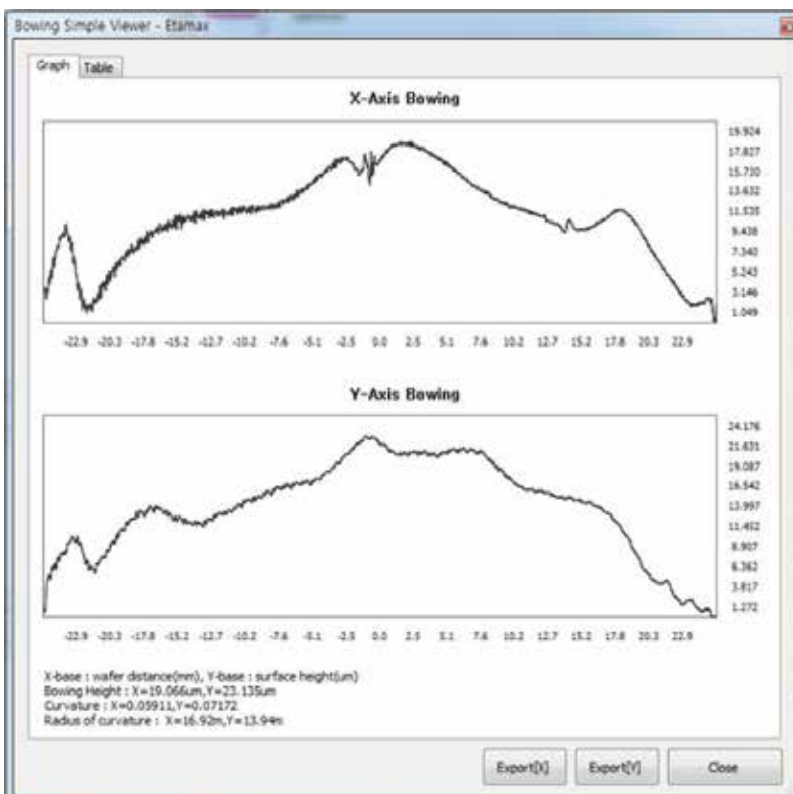


Bowing Height

X = $\sim 19 \mu\text{m}$
 Y = $\sim 23 \mu\text{m}$

AlGaN on AlN/Sapphire Template

Layer Structure	Thickness AlGaN / AlN	Al _x Ga _{1-x} N Composition	AlN (arcsec)		AlGaN (arcsec)		Mapping
			(002)	(102)	(002)	(102)	
AlGaN / AlN / Sapphire	0.798um / 2.94um	62.3 %	156	479	321	455	5 points
AlGaN / AlN / Sapphire	0.955um / 2.83um	67.6 %	146	377	278	357	5 points
AlGaN / AlN / Sapphire	1.15um / 2.87um	65.2 %	179	389	310	399	5 points
AlGaN / AlN / Sapphire	1.61um / 2.83um	65.0 %	168	386	308	441	5 points

AlGaN on AlN/Sapphire Template: PL Mapping Data

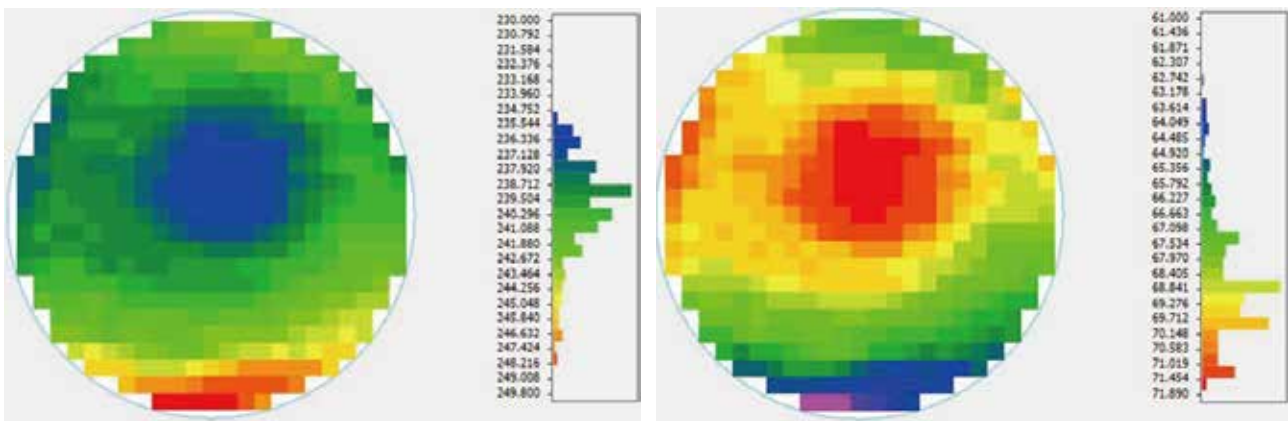

Wavelength

Al Composition